

# COTTON FIBER QUALITY MEASUREMENT USING FRAUNHOFER DIFFRACTION

Ayodeji Adedoyin, Changying Li

Department of Biological and Agricultural Engineering, University of Georgia, Tifton, GA

## Abstract

Properties of single cotton fibers may provide a better way for cotton processors and producers to predict and characterize the properties of a bulk sample of cotton. In this work a relatively simple and easily replicable approach is developed to determine the diameter (“ribbon-width”) of single cotton fibers and this knowledge may then be used to characterize single cotton fiber quality parameters such as fineness, maturity, and micronaire. The overall objective of this research was to conduct a fundamental study of the optical properties (light diffraction) of individual cotton fibers with the interaction of a monochromatic light beam. Diffraction patterns generated from the interaction of each cotton fiber and the laser light are captured by using a linear CCD camera. Each fiber was measured at multiple points. The diameter of each fiber was determined from the distance between consecutive fringes of the diffraction patterns generated. Preliminary results show that the average fiber diameters obtained fall within the range of 15-20 $\mu\text{m}$ , which is approximately the expected range for a cotton fiber. The shape of the diffraction patterns observed is consistent with the shape of the theoretical solution of light obstructed by a thin wire/fiber. Moreover, the distribution of the diameters follows the tendency of a normal distribution. The approach used in this research may be integrated with existing cotton fiber measurements systems such as HVI and AFIS systems to provide a better characterization of cotton fiber quality.

## Introduction

The use of cotton for a particular application depends on the quality of the cotton. The quality of cotton depends on the cotton fiber properties, namely length, length uniformity, strength, fineness, maturity, trash content, leaf grade, color grade, preparation, and extraneous matter. Currently, the methods used to characterize the quality of cotton fibers involve analyzing the properties of bulk samples. The properties of single cotton fibers if needed are then extracted from the properties of the bulk samples. Although, analyzing the properties of bulk samples of cotton fibers may provide a cheap and rapid technique to characterize cotton fiber quality, it may not however provide the properties of individual cotton fibers. Fundamentally, knowledge of a single cotton fiber should be used to characterize the properties of a bulk sample of cotton.

One method to analyze individual fibers may be to develop an optical sensing tool that can be used to characterize single cotton fiber quality as proposed by Thomasson et al. (2009). Such an optical approach has been developed in this study. Assuming that cotton producers and processors have the same method of characterizing cotton fiber quality, producers can prevent the amount of discount they may receive by turning in cotton fibers they know have a high quality and processors will not need a set of

multiple devices to determine the quality of a bale of cotton. Variations in the quality of cotton fibers exist between different portions of a cotton field, from plant to plant, and even within the same plant. Moreover, the quality of fibers on a single seed may vary in length, shape, thickness, and maturity as described in Jost (2005). By studying individual cotton fibers from different parts of a seed, different plants, and different locations on a field, it may be possible to determine the causes of the variation in cotton fiber quality and this is similar to the work done by Cui et al. (2003).

The overall objective of this research project was to conduct a fundamental study of the optical properties of individual cotton fibers with the interaction of a laser beam and how this interaction can be related to cotton fiber quality parameters, such as fineness, maturity, and micronaire. More specifically the experimental approach used in this work may be used to develop a simple and inexpensive optical sensing tool to rapidly and accurately measure single cotton fiber quality parameters, investigate the anisotropic nature of the diameter of single cotton fibers by analyzing multiple points along each fiber, and to develop a software program that may be used to automatically characterize the quality of single cotton fibers.

## **Materials and Methods**

The schematic of the experimental setup used in this work to study the optical properties of single cotton fibers is shown Figure 1. The experimental setup, which was assembled in Advanced Fiber Quality Sensing Laboratory (AFQSL), consists of a light source, polarizing lenses (P1), an iris (I1), a single cotton fiber holder (S1), a collecting lens (CL), and a linear CCD camera (CCD).

The cotton samples used for this study were obtained from the USDA classing office and from the University of Georgia Micro Gin facility. Eight (8) cotton varieties with different micronaire values were obtained and used for this work. Specifically, the cotton fiber varieties are Lint 101 (BCS 614), Lint 108 (ST 5327), Lint 110 (DPL 0924), Lint 203 (PHY 370), Lint 205 (DPL 901), Lint 209 (BCS 0727), USDA 2.6, and USDA 5.47. A total of fifty-six (56) fibers (seven (7) fibers from each variety) were used for the preliminary results presented in this paper. Over 50 diffraction patterns at different points along the axis of each fiber were measured. By measuring multiple points along each fiber the anisotropy (non-uniformity) of the diameter of cotton fibers can be studied and analyzed.

The diameter of a single cotton fiber can be computed from the diffraction pattern generated by illuminating it with a light source. Figure 2 shows a theoretical diffraction pattern simply to illustrate how the diameter of a fiber can be computed from a diffraction pattern. The normalized intensity (in arbitrary units) is plotted against the length of the observation plane. In order to compute the diameter of a fiber, the dark fringes (low peaks) are identified on either side of the center peak (center fringe). The dark fringes are identified with circular symbols in Figure 2. The distance between consecutive dark fringes are then calculated. A similar technique was used to calculate the diameter of wider wires/fibers in Khodier (2004). Ideally the distance between the

first and second order fringes should be the same for the distance between the second and third order fringe and this applies for higher order fringes. In some cases we were only able to observe first and second order fringes on either side of the center fringe.

## Results and Discussion

In Figure 3, we present diffraction patterns generated as a result of illuminating with the laser light at single point along the axis of a single cotton fiber. Although the figures show diffraction patterns for the Lint 101, Lint 209, USDA 2.6, and USDA 5.47 varieties, similar patterns were observed for the other four cotton varieties used in this work. Figure 3 shows the normalized intensity of the diffraction pattern versus the position along the observation plane. The symbols in Figure 3 represent the experimental data and the solid lines are the denoised signals. The noisy nature of the experimental data obtained presented a challenge (determining the precise location of the high and low peaks) in interpreting the diffraction patterns therefore the experimental signals were denoised by using a MATLAB denoising function. As the figures show, the denoised signals agree well with the experimental data.

The selected diffraction patterns presented in Figure 3 are in good agreement with the theoretical diffraction pattern (Figure 2). As expected, we observed a high peak (center fringe) in the diffraction pattern as well as first and second order fringes on either side of the center fringe. In some cases we were able to observe what may appear to be higher order peaks as shown in Figure 3, but further work is needed to verify if indeed these correspond to higher order fringes. It would appear from Figure 3 that there are two center fringes in each diffraction pattern but this is not the case. In order to prevent the CCD line camera from being saturated, the portion of the observation plane where the center fringe was incident on the CCD was blocked out. The width of the block out material used was chosen so as to not block out the entire center fringe but leave some portion unblocked to verify that the shape of the diffraction patterns generated agreed with the theoretical solution. This explains why the diffraction patterns appear to have two center fringes.

It was observed that the height of the higher order peaks (fringes) is not uniform from pattern to pattern and this may be due to the nature of the cotton fiber itself. Further analysis of the preliminary results presented in this work will be needed to determine the cause(s) of the change in shape of the diffraction patterns. This change in shape of the diffraction patterns was observed to vary within the same cotton variety as well as between different cotton varieties. Not all diffraction patterns generated at each point along a single cotton fiber generated the same results presented in Figure 3. In some cases there were no diffraction patterns noticeable in the observation plane even though the cotton fiber was clearly illuminated by the laser beam. The inability to measure diffraction patterns may be attributed to two main reasons. The width of the CCD line camera was so small that any slight deviation of the diffraction pattern from the detecting portion of the camera will result in diffraction patterns that cannot be observed. Furthermore, from the first point it can be deduced that the angle at which the diffraction pattern is incident on the CCD camera is very important. In order to relax

this limitation(s) it may be useful to use a two-dimensional observation plane as opposed to a line observation plane. In this way the deviation of the diffraction pattern will be observed irrespective of the angle of deviation.

In Table 1 we present the average diameter for each cotton variety obtained by using our laser diffraction technique. These preliminary results seem encouraging because the average diameters fall within the expected range for cotton fibers in general, that is, between 15-20 $\mu\text{m}$ . For more accurate results, more fibers will need to be tested to form a better representation of the particular variety. The average diameters obtained for each variety are too close to each other to be used to differentiate between the cotton varieties but all the varieties used for this study have different micronaire values. If we can relate the measured diameter of each fiber to the micronaire values, then we may be able to differentiate each variety by using our optical method.

A single cotton fiber or a sample of cotton fibers observed under a microscope reveals that the diameter of a cotton fiber is not uniform along the fiber axis. A distribution of average diameters measured for the Lint 108 cotton variety is presented in Figure 4. The expected results from such a study would suggest that the shape of such a distribution should show a normal (Gaussian) distribution. This may be the case if more fibers and more points are measured. Nonetheless, encouraging results can be seen from Figure 4. The figure shows that most of the points measured were about the average (15  $\mu\text{m}$ ). The values of the diameters seem to fall off on either side of this average value. Although not the expected normal distribution, the trend seen in the figure suggests the same trend as that of a normal distribution. A very similar trend may be deduced from Figure 4 but further work is needed to make such a concrete generalization.

## **Conclusion**

The optical properties of single cotton fibers was studied and analyzed by illuminating single cotton fibers with a monochromatic laser light. The diffraction pattern generated as a result of the interaction between the laser light and each single cotton fiber was analyzed and presented. A relatively simple methodology was used to measure the average diameter (ribbon-width) for each cotton variety used in this work. Diffraction patterns generated are in good agreement with the theoretical solution even though the theoretical solutions are for fibers illuminated by uniform light and not Gaussian light beams as the approach used in this study. Numerical algorithms and techniques have been developed to detect the dark fringes within each diffraction pattern and to compute the average diameter of a single point along the fiber axis. Diameter measurements obtained fall within the expected range (15~20  $\mu\text{m}$ ) for the diameter of a cotton fiber.

More work is needed to determine the quality parameters of the single cotton fibers. Since the micronaire values for each cotton variety used are known then in order to validate the methodology an algorithm to compute micronaire values is paramount in the next stage of this work. The distribution of diameters for each cotton variety follows the trend of a normal distribution and more samples will be tested to provide a more accurate generalization of a cotton variety. Obtaining consistent diffraction patterns for

every point along a fiber may be accomplished by using a two-dimensional observation plane instead of a line CCD camera which may not be able to detect diffraction patterns that are not along the same axis.

It can be deduced from the preliminary results that the current methodology is capable of determining the diameter of single cotton fibers. A correlation between the measured diameter and cotton fiber quality parameters, specifically fineness, maturity, and micronaire will be developed to validate the accuracy of our technique. The diameter of single cotton fibers was verified to be anisotropic in nature confirming the presence of convolutions along the axis of the single fibers. Research currently underway will continue to optimize numerical techniques developed and to develop numerical models to determine the fineness, maturity, and micronaire values by illuminating single cotton fibers with a laser light.

### **Acknowledgments**

The authors sincerely wish to thank Cotton Incorporated. This work will not have been possible without their full support.

### **References**

- Butler D. J., and G. W. Forbes. 1998. Fiber-diameter measurement by occlusion of a Gaussian beam. *Applied Optics* 37: pp. 2598-2607.
- Cui X., M. W. Suh, and P. E. Sasser. 2003. Estimating Single Cotton Fiber Tensile Properties from the Load-Elongation Curves of Slack Bundles. *Textile Res. J.* 73: pp. 1066-1070.
- Glass M. 1998. Diffraction of a Gaussian beam around a strip mask. *Applied Optics* 37: pp. 2550-2562.
- Jost P. 2005. *Cotton Fiber Quality and the Issues in Georgia*. The University of Georgia.
- Khodier S. A. 2004. Measurement of wire diameter by optical diffraction. *Optics & Laser Technology* 36: pp. 63-67.
- Smithgall D. H., L. S. Watkins, and R. E. Frazee Jr. 1977. High-speed noncontact fiber-diameter measurement using forward light scattering. *Applied Optics* 16: pp. 2395-2402.
- Thomasson, J. A., S. Manickavasagam, and M. P. Mengüç. 2009. Cotton Fiber Quality Characterization with Light Scattering and Fourier Transform Infrared Techniques. *Applied spectroscopy* 63: pp. 321-330.

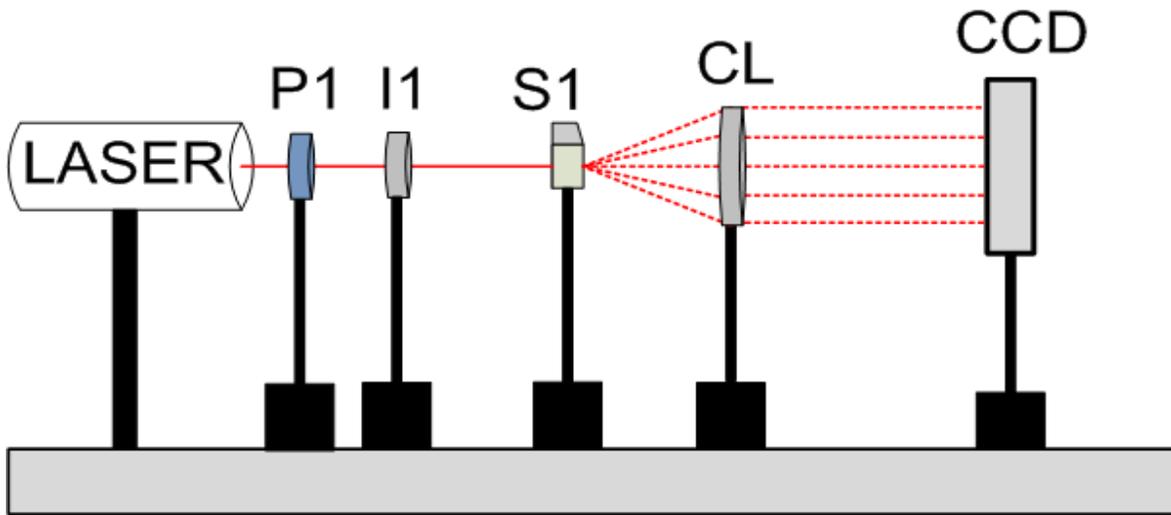


Figure 1. Schematic of experimental setup used to implement tabletop Fraunhofer diffraction.

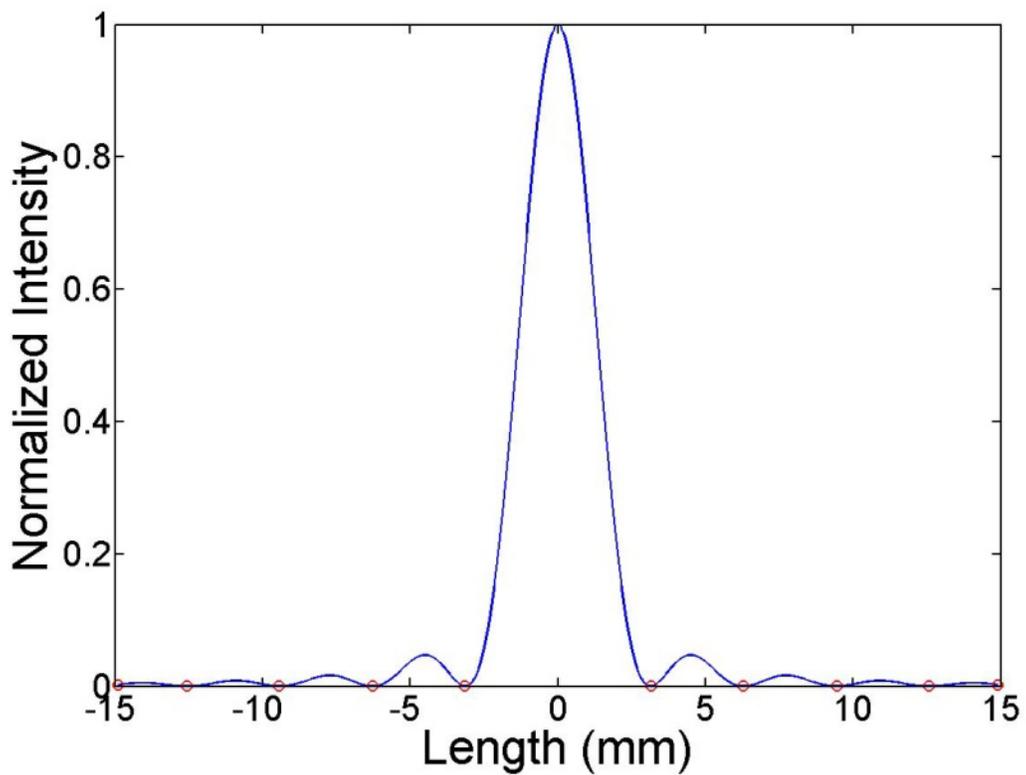


Figure 2. Theoretical solution for diffraction pattern generated by illuminating a single fiber.

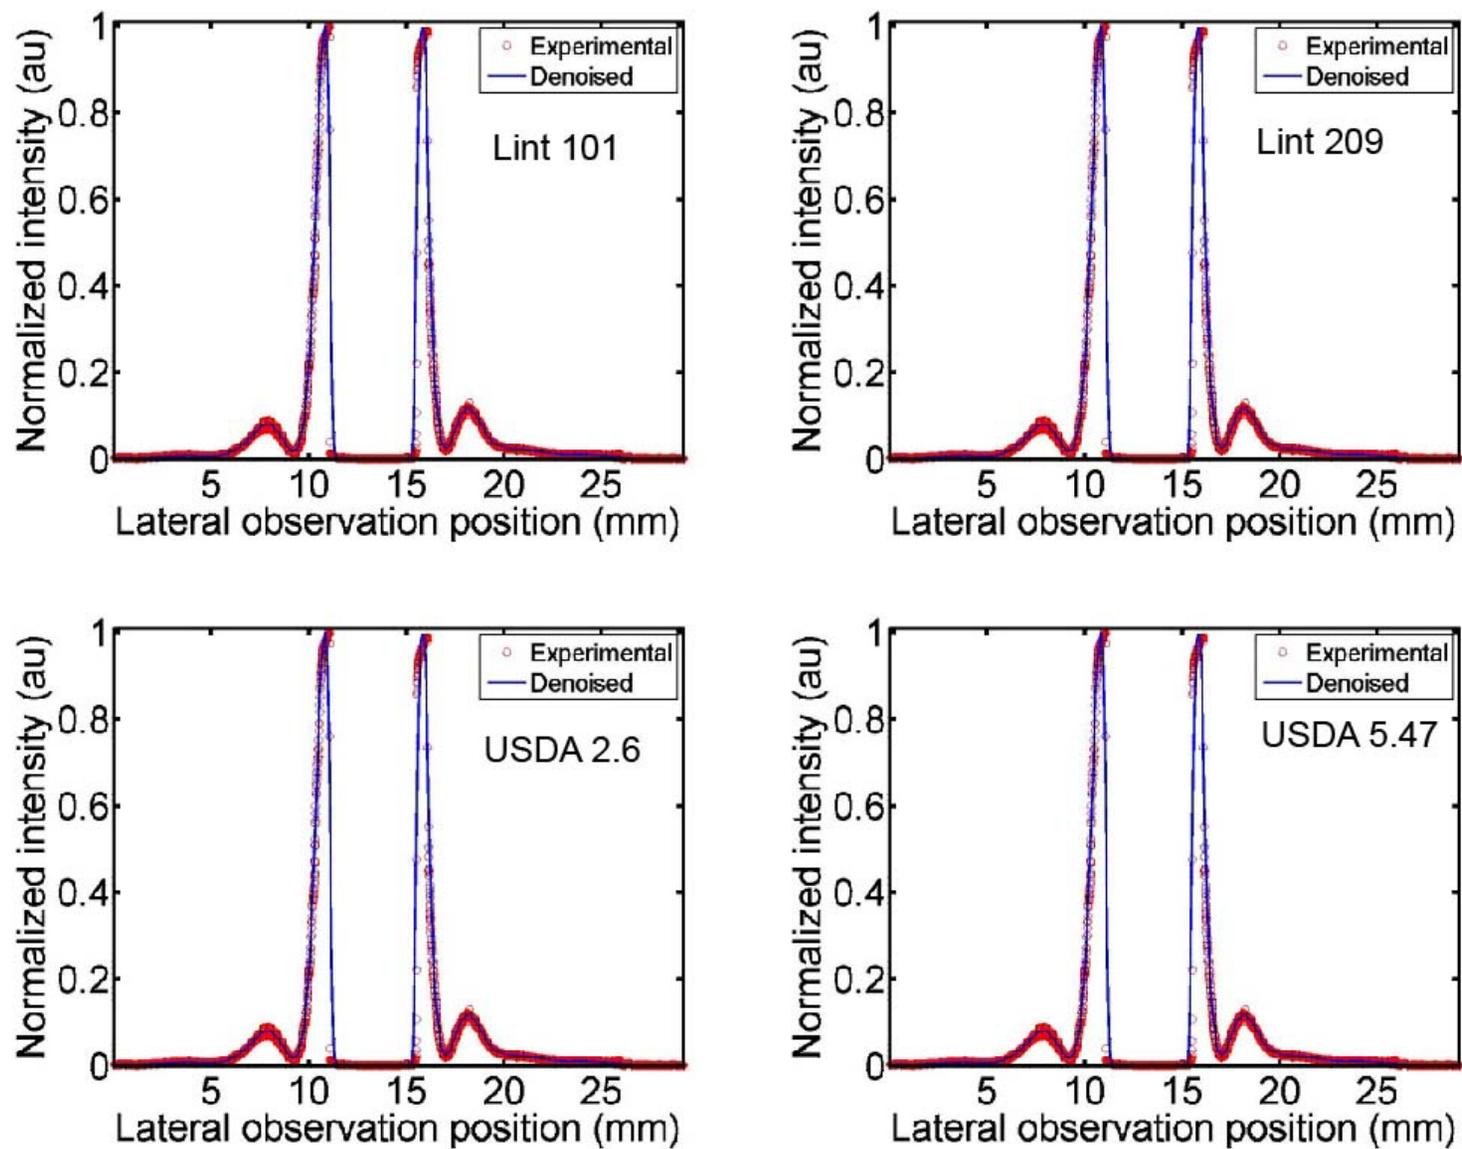


Figure 3. Sample diffraction patterns generated by illuminating a single cotton fiber of four cotton cultivars.

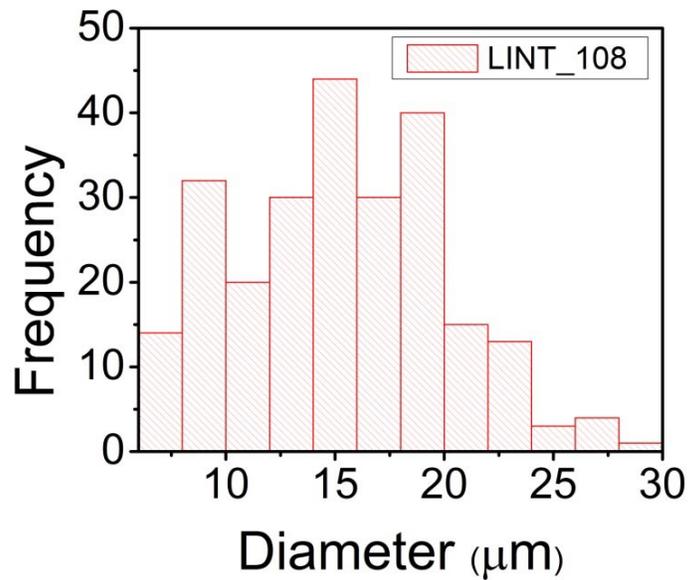


Figure 4. Distribution of cotton fiber diameters for the Lint 108 variety.

Table 1. Average diameter computed from the resulting diffraction pattern of each cotton variety.

Cotton Variety	Average Diameter (μm)
LINT 101	16.517
LINT 108	15.521
LINT 110	15.354
LINT 203	15.609
LINT 205	17.182
LINT 209	16.578
USDA 2.6	15.195
USDA 5.47	15.072